

Gear Peening: The Intense Story

Kumar Balan, Product Engineer, Wheelabrator Group

Kumar Balan is employed by the Wheelabrator Group, Burlington, Ontario (Canada) in applications, sales and marketing. His experience includes design, applications, sales and technology transfer for companies such as Wheelabrator and Pangborn in India and North America. From 1995–2000, Kumar worked for Blastworks Inc., a Canadian company that specialized in automated airblast machinery. After a detour in industrial automation relating to robotic material handling systems and CNC fabrication machinery, Kumar returned to the Wheelabrator Group in Burlington, Ontario.

Automotive designers have traditionally relied on the advantages of shot peening of transmission parts to enhance their useful life. Commonly, shot peening machines are found post-heat treat and at the end of a production process for critical parts, such as ring and pinion gear sets.

In peening circles, it is common knowledge that indentation of a metal surface by bombarding it with metal projectiles at high speed induces compressive stresses in the layer. With this as the basis of any shot peening application, it is not unusual to find any “available” shot peening machine being put to active use topeen critical components. However, premature transmission failures and recalls are now prompting gear manufacturers to re-evaluate this seemingly simple process and develop it along the lines of an “application-based” approach for their peening needs.

Mechanism and Effects of Shot Peening

Impingement of metallic media (shot or cut wire) causes plastic deformation on a part surface. This extends the superficial layer, creating compressive stresses underneath and providing a balance to the tensile stresses. This residual compressive stress delays the formation of fatigue cracks, thereby increasing the useful life of a component.

Continuous impact of peening media on gear surfaces (after heat treatment) also transforms the residual austenite to martensite. This increases the hardness of the base material and induces compressive stresses.

With specific reference to gears, maximum shear stress appears

at the root areas and in the transition radius. Increasing loads are experienced in the drive and coast faces. Therefore the focus of peening gears is on:


- Drive face,
- Coast face, and
- Root areas.

Finish requirements, namely intensity and coverage, vary from one gear set to the other and are dependent on the final application. Whereas coverage is purely a visual check, intensity is a measure of deflection of a representative strip of spring steel (commonly called the Almen Strip).

continued



Mechanism and Effects of Shot Peening

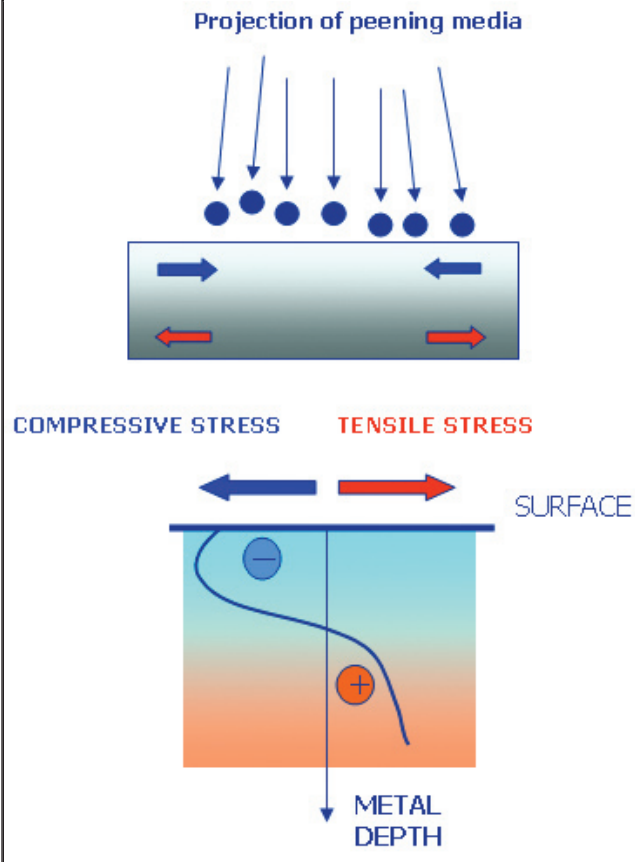

Centrifugal Blast Wheel



Intensity Measurements

Part Verification Tools (PVT), such as the one shown on page 23, are designed to hold test strips in strategic locations. Test strips in these locations simulate areas of the part where intensity requirements—and therefore measurements—are critical.

Intensity ranges could be anywhere from 0.015 to 0.030 on the 'A' scale, depending on the application. Coverage requirements could range from 100% to 200%. The above results can be achieved through a limited choice of peening techniques, each with its own distinct advantages over the other. These are:

- Using centrifugal blast wheels,
- Using pressure blast nozzles, and
- Using hybrid machines (combinations of wheels and nozzles).

Media Propulsion Types

Centrifugal blast wheels are superior to other media propulsion techniques when productivity is in consideration. The media flow generated by a blast wheel covers a larger surface area than a blast nozzle. However, the limitation is usually set by the size of the gears being peened. In cases of smaller gears with narrow root areas, it may be required to employ multiple blast wheels positioned at strategic angles to achieve adequate coverage.

Alternatively, multiple direct pressure blast nozzles, each focusing on specific tooth areas provide targeted blast coverage. Both types of media propulsion systems are in wide use, though blast nozzle peening systems are gaining popularity in relatively newer peening systems.

Process Variables

Though not very common, hybrid systems (combination of blast wheel and nozzle propulsion systems) offer the benefits of higher productivity with the wheel and “touch-up” peening in required areas within the same machine using a pressure blast nozzle.

Regardless of the peening technique used, achieving the intensity targets in a repeatable and consistent fashion is the primary goal of any operation. It is therefore important to understand the critical variables that alter the final results in a peening process. They are:

Centrifugal Blast Wheel

- Blast Wheel
- Wheel HP
- Wheel Speed
- Blast Angle
- Wheel positioning
- Control cage movement

Direct Pressure Nozzle

- Blast Nozzle
- Nozzle Size
- Blast Pressure
- Blast Angle
- Nozzle Movement
- Multiple Nozzles

Each of the above process variables impacts the final result as follows:

- The diameter of the blast wheel determines the tangential velocity of the projectile (blast media). Being in direct proportion, a 17.5" diameter wheel generates a greater velocity and therefore higher peening intensity than a 14" diameter wheel at the same speed.
- Horsepower of the wheel simply determines the amount of media propelled by the wheel.
- Wheel size works in conjunction with the wheel speed

$(\pi \cdot D \cdot N)$ to achieve the desired velocity and thereby the intensity. Blast wheel peening machines can be equipped with variable frequency drives to vary the wheel speed and therefore the velocity.

- Blast wheels are always mounted in a permanent and rigid location in the blast cabinet. However, blast pattern alterations, if required, are achievable by altering the control cage settings. The control cage location determines the exact point of blast media discharge from the blast wheel.

In a direct pressure blast nozzle system,

- The blast pressure is analogous to the wheel speed in a wheel-type system. Higher blast pressures help achieve higher intensities. Blast pressure in a sophisticated gear peening system is usually monitored in a closed-loop feedback arrangement using a proportional regulator. Any deviation from the pre-set pressure value triggers an alarm to shut the machine down.
- The nozzle sizes determine the amount of media propelled toward the part. The target factor being relatively higher in a nozzle-type system, all the energy dispensed through the blast media is directly applied towards achieving the required intensity.
- Blast nozzle movements are possible by mounting the nozzle(s) on multi-axis nozzle manipulators. These manipulators, with the assistance of servo drives and motion controllers, are capable of providing interpolated motion to the blast nozzle(s), which results in the blast nozzle following the part contour. Following the profile of a pinion or ring gear results

in a consistent stand-off distance and thereby in more repeatable results.

When peening a set of pinion and ring gears simultaneously, attention must be given to the fact that tooth angles vary significantly within the set. Therefore, in a nozzle-style system, it becomes important to rely on independent nozzle settings in order to achieve desired results on the pinion and ring gears.

This is achieved using a dedicated nozzle carriage for the ring and pinion gears respectively.

Other process variables affecting peening results include:


- Media flow rate,
- Size of media, and
- Consistency of size.

Media flow rate is controlled using a commercially available flow control valve (for example, MagnaValve, manufactured by Electronics Inc.). Flow control valves are provided at the feed side of the blast wheel or at the pressure vessel outlet in case of a blast nozzle system.


A vibratory classifier classifies the peening media into oversize, right and undersize/fines. A combination of two sieves ensures that a consistent size of peening media is available for every cycle.

Size of steel shot (or cut wire) plays an important role in deter-

continued

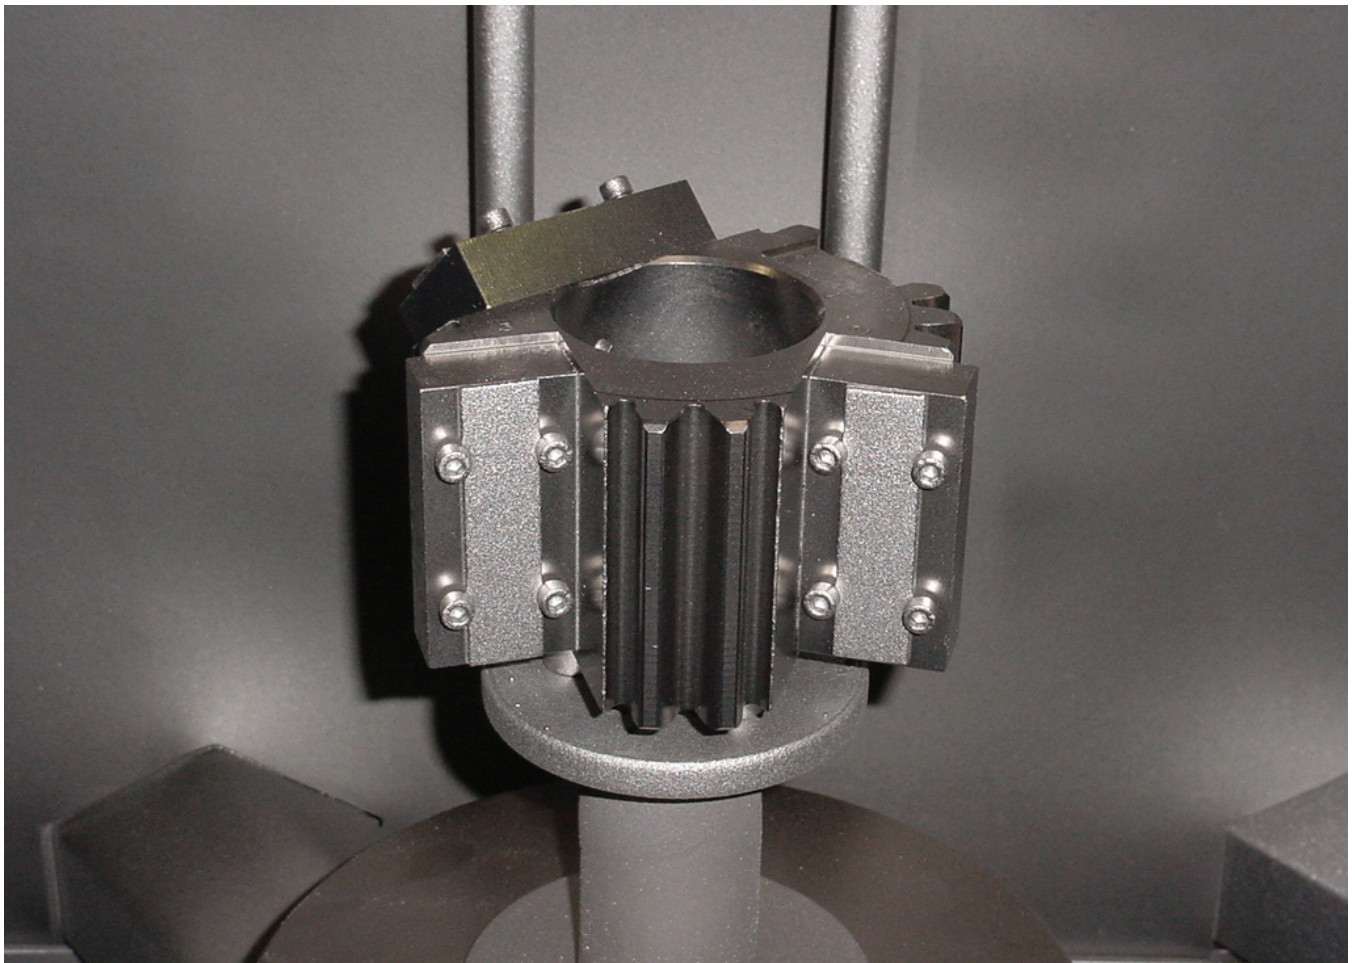

Vibratory Classifier

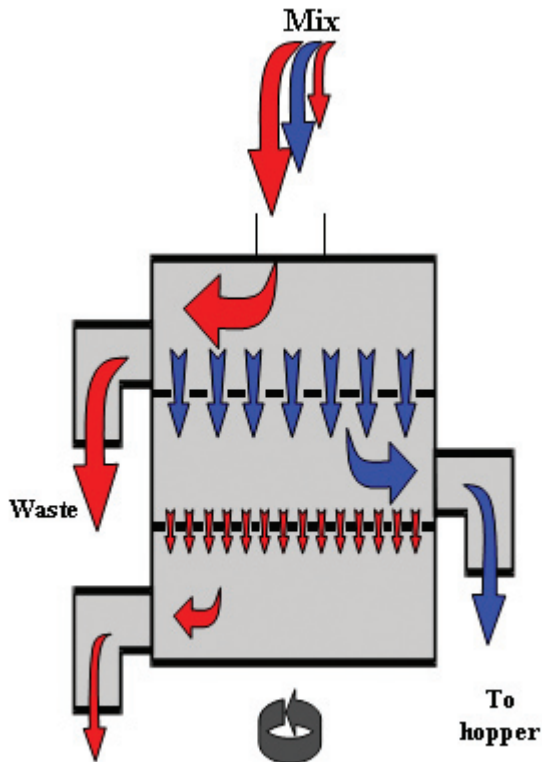

Small, broken shot and dust

determining coverage and peening cycle time. The following general rules apply: (a) smaller sized shot allows higher stress on immediate surfaces, (b) larger sized shot provides stress in material depths and (c) diameter of shot should be less than half the smallest radius in the part.

Summary

Gear peening systems have evolved over the past years. It is now possible to accord the same sophistication to the peening of gears in high volumes as is available to the peening of an aircraft landing gear. In both cases, the thrust is on repeatability and consistency of results.


Mechanical process variables in conjunction with sophisticated yet simple controls provide great flexibility in setting the process to achieve the desired peening effect on the part.

Contemporary automotive engineers are no longer restricted to using a traditional blast wheel machine or even just a blast nozzle machine for their peening needs. Hybrid systems offer the benefits of both systems in an integrated platform designed to cater to specific needs. ■

For more information:

Wheelabrator Inc.
1606 Executive Dr.
LaGrange, GA 30240
Phone: (404) 884-6884

Setup for Peening Ring & Pinion Gears

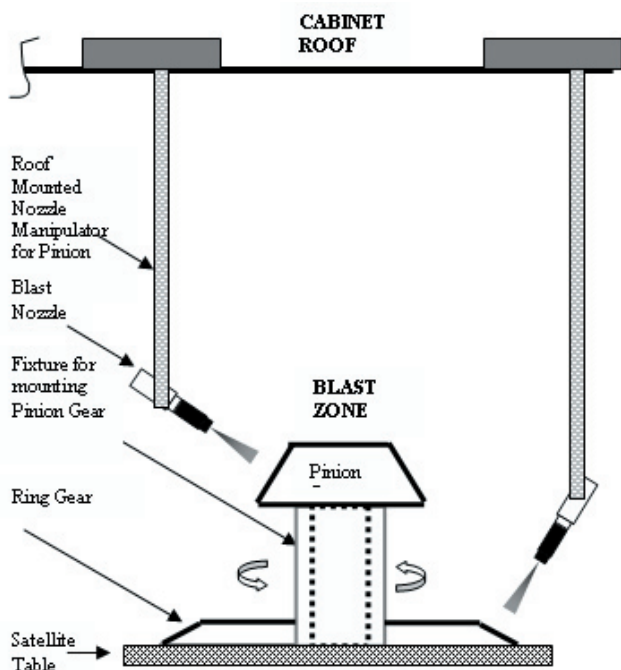

World's Best Gear Boxes Working in 48 Countries All Over the World

Power Engineering & Manufacturing, Ltd.

EFFICIENCY THROUGH ENGINEERING & INGENUITY


CUSTOM MADE GEAR BOXES *
OVER 380 MODELS *
OVER 460 APPLICATIONS AND GROWING




Standard Gear
100% Fatigue Life



MEGAGEAR®
260% Fatigue Life


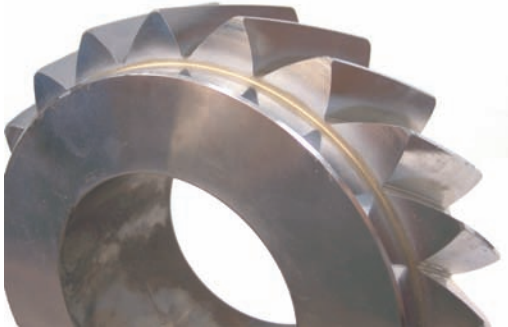


UNIMEGAGEAR®
345% Fatigue Life

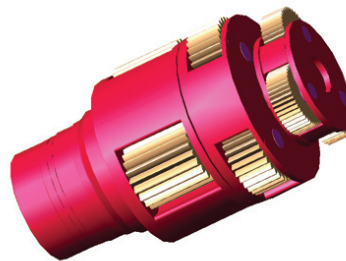

**Builder of the Most Powerful
Gear Teeth and Planetary Gear
Boxes Working All Over the
World**

Planetary Gear Box
2500 lb Flywheel to Decrease Vibrations

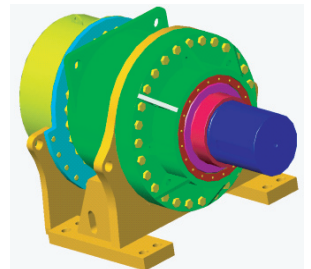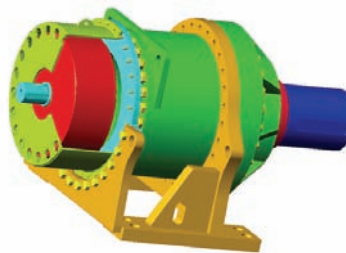

2635 WCF&N Dr. * P.O. Box 4055 * Waterloo, Iowa 50704

Phone (319) 232-2311 FAX (319) 232-6100

E-Mail info@pemltd.com * <http://www.pemltd.com>



Interested in our MEGAGEAR® technology to save you **material** and **labor**?
Achieve **increased fatigue life**? Contact PEM for more information.